

Activation of ZnCl₂ and KOH Carbon from Bark of Salak Wedi as a Material for Making Supercapacitor Electrodes

By Aprillia Dwi Ardianti



Activation of ZnCl₂ and KOH Carbon from Bark of Salak Wedi as a Material for Making Supercapacitor Electrodes

Aprillia Dwi Ardianti

Mechanical Engineering Department, Faculty of Science and Technology, Universitas Nahdlatul Ulama Sunan Giri, Bojonegoro 62115, Indonesia

Email Correspondence: aprilliadwia@unugiri.ac.id

16

Article Info

Article History

Received: 22 February 2022

Revised: 28 February 2022

Published: 25 March 2022

Keywords

Salak wedi, ZnCl₂, KOH, Elektrodes

Abstract

13
Activation of ZnCl₂ and KOH Carbon from bark of salak wedi as a material for making supercapacitor electrodes An activated carbon is a potential material that can be used as electrodes in super capacitors. It has a higher energy density than batteries and fuel cells, and a higher power density than conventional capacitors. This research was carried out using activated carbon powder from the bark of salak wedi which was physically activated at a temperature of 500° C. The activation stage is chemical activation using ZnCl₂ and KOH activators, after which gradual activation is carried out, namely: carbon ZnCl₂ + KOH (s) and carbon KOH + ZnCl₂ (s). So that with the gradual activation, 4 variations of the sample will be obtained, namely: ZnCl₂, 17 H, carbon ZnCl₂ + KOH (s) and carbon KOH + ZnCl₂ (s). The physical characteristics of the activated carbon from the bark of salak wedi were analyzed using a Scanning Electron Microscope (SEM) to see its powder morphology. While, X-ray diffraction (XRD) is used to examine the structure of the bark of activated carbon that has the potential to make electrodes of super capacitors. The results of SEM with graded activation had fewer pores, were not evenly distributed and tended to agglomerate compared to the activated carbon sample of salak bark which was activated once. This research has not yet reached the stage of making electrodes, it is hoped that in future research it can be applied to electrodes so that data such as capacity, voltage, current and others are obtained.

© 2021 Creative Commons Atribusi 4.0 Internasional

Citations: Ardianti, Aprillia D. (2022). Activation of ZnCl₂ and KOH Carbon from Bark of Salak Wedi as a Material for Making Supercapacitor Electrodes. Science Education and Application Journal, 4(1), 37-45.

INTRODUCTION

Supercapacitors are electrical energy storage devices that have some characteristics such as a longer life time compared to the batteries as well as simple principles and models, short charging times, high power density, safe because they do not contain corrosive materials and less poisonous materials (Fitriana, 2014). Super capacitors can provide at least 1000 times more energy than dielectric capacitors and 10 times more power than batteries and super capacitors have a long life cycle of more than 500000 cycles (Zhou et al., 2015). Activated carbon is one of the kind of materials that has been widely used because it has a high surface area, chemical resistance, good electrical conductivity and an affordable price (Mardwianta, 2017). Activated carbon is a material that contains a large amount of free

carbon, where the free carbon has a high absorption capacity and has pores that increase its absorption due to its reactions with chemicals before or after carbonization (Waluyo et al., 2017).

Many studies on activated carbon have been carried out before this study. A preliminary study on the effect of temperature and concentration on carbon activation process from Halaban wood using ZnCl₂ and KOH has been carried out by Amanah with the results of the absorption efficiency of the two largest activators being ZnCl₂ with a value of 95.1% and KOH of 93.3% (Permata et al., 2019). The manufacture of activated carbon from coconut shells to reduce ammonia levels with KOH, NaCl and HCl activators was carried out by Nisa Nurhidayanti (Nurhidayanti, 2020). Research on variations in holding time of activated carbon activation temperature from kluwak shell an electrode on a super capacitor with results that the longer holding time, the smaller the pore size, the larger the surface area and the greater the capacitance (Habibah, 2016). The analysis on the differences of the activator materials in the manufacture of super capacitor electrodes from coconut shell charcoal get the results of increasing the value of specific capacitance with chemical activation using KOH activator (Susanti et al., n.d.-a; Taer et al., 2018)

The factor that affects the amount of absorption of an activated carbon is the surface area. Various methods can be used to increase the surface area of activated carbon (Kearns et al., 2014). One of the ways is the use of activators. In addition, the structure of activated carbon also determines the surface area of activated carbon (Sayğlı & Güzel, 2016). The structure of activated carbon is basically amorphous. With activation treatment on carbon can also increase the crystallinity of activated carbon (Ghosh et al., 2019). The crystallinity of activated carbon affects the surface area. With regularity on the crystal structure and Nano size makes a wider surface area (Jain et al., 2018)

Based on the references of previous studies, the researcher wanted to conduct research with several activation treatments on salak bark carbon and determine the morphology and structure of activated carbon which has the potential to be used as electrodes in super capacitors. Salak (*Salacca edulis* Reinw) comes from Southeast Asia (Mazumdar et al., 2019). This fruit has a shape resembling an egg. The skin of the fruit is brown and looks like snakeskin. Salak contains three pieces of seeds covered with white flesh. In Indonesia, there are many cultivars of salak, but most of them have an astringent taste. The skin of the fruit is covered with scales, the appearance looks like reptile skin. The edible part is the white flesh which is aromatic and translucent, tastes like a mixture of pineapple and banana. Each fruit contains 1 to 3 dark brown seeds. The flesh of the fruit is edible and consists of three lobes (Deiningner et al., 2002). After peeling, the skin becomes waste and it is used as raw material for the manufacture of activated carbon in this study.

Activated carbon is an amorphous carbon from flat plates composed of C atoms covalently bonded in a flat hexagonal lattice with one C atom at each corner and has a hollow surface and a layered structure. High quality activated carbon is characterized by high surface area and pore volume (Hartanto & Ratnawati, 2010). The process of making activated carbon is carried out in two stages. The first stage is the carbonization process of raw materials which is carried out to produce charcoal and the second stage is an activation process to remove the hydrocarbons that coat the surface of the charcoal so that the porosity increases (Lempang et al., 2011).

The factor that affects the amount of absorption of an activated carbon is the surface area. Various methods can be used to increase the surface area of activated carbon. One way that is often used is the use of activators. In the activator research in stages, it produces a higher capacitance value. This capacitive property is related to a higher carbon surface area, whereas in carbon that only one activation is carried out it results in a lower capacitive

property (Jin et al., 2013). Chemical activation is generally done by conditioning the base material with a strong dehydrating agent, such as phosphoric acid or other chemicals such as HNO₃, ZnCl₂, CaCl₂ (Masriatini, 2018). According to its use, activated charcoal is classified as a chemical product and not an energy source such as charcoal or charcoal briquettes. Advanced charcoal processing technology into activated charcoal will provide great added value in terms of use and economic value (Hendra, 2007). The activation process is an important thing to note in addition to the raw materials used. Activation is a treatment of charcoal that aims to enlarge the pores, namely by breaking the hydrocarbon bonds or oxidizing the surface molecules so that the charcoal undergoes changes in properties, both physical and chemical, namely the surface area increases and affects the adsorption power (Ajayi et al., 2009). The activators used in this study were ZnCl₂ and KOH. The research is analysis of the structure of salak wedi activated carbon as a material for making supercapacitor electrodes. The activation stage is chemical activation using ZnCl₂ and KOH activators, after which gradual activation is carried out, namely: carbon ZnCl₂ + KOH (s) and carbon KOH + ZnCl₂ (s). So that with the gradual activation, 4 variations of the sample will be obtained, namely: ZnCl₂, KOH, carbon ZnCl₂ + KOH (s) and carbon KOH + ZnCl₂ (s) (Susanti et al., n.d.-a)

METHODS

Method and Procedure

Salak bark is carbonated in a furnace which is flowed with inert gas at a temperature of 500°C for approximately 1 hour which aims to omit volatile substances in the bark. Then the bark char-coal is rested to cool in a desiccator. After that, the bark charcoal produced was ground and sieved through a 100 mesh sieve and retained on a 200 mesh sieve to produce carbon powder (Bagheri & Abedi, 2009). The resulting carbon powder is then mixed with solid activator with a mass ratio of carbon powder's mass and activator, 1:4. The solid activator was dissolved with distilled water to a concentration of 20%. The carbon powder was then mixed into the solution and shaken for 20 hours with a magnetic stirrer. The activated carbon powder was then oven-dried then washed with distilled water and dilute HCl solution until the pH of the washing water reached 6-7 (Bagheri & Abedi, 2009). The washed carbon powder is then dried again in the oven. The activation stage is chemical activation using ZnCl₂ and KOH activators, after which gradual activation is carried out, namely: carbon ZnCl₂ + KOH (s) and carbon KOH + ZnCl₂ (s). So that with the gradual activation, 4 variations of the sample will be obtained, namely: ZnCl₂, KOH, carbon ZnCl₂ + KOH (s) and carbon KOH + ZnCl₂ (s) (Susanti et al., n.d.-a). The scanning electron microscope characterization was carried out to determine the surface morphology of the bark's carbon the identification of the pore distribution. The scanning electron microscope was tested with four magnifications, those are 500x, 1000x, 5000x and 10.000x (Kiswar, 2014; Susanti et al., n.d.-b). As well as testing using XRD to see the structure of bark's activated carbon which has the potential to be used as electrodes in super capacitors.

RESULTS AND DISCUSSION

The formation of pores on the activated carbon of salak bark is shown by the surface morphology of the activated carbon from the Scanning Electron Microscope (SEM) which is shown in Figure 4 with a magnification of 2500 times.

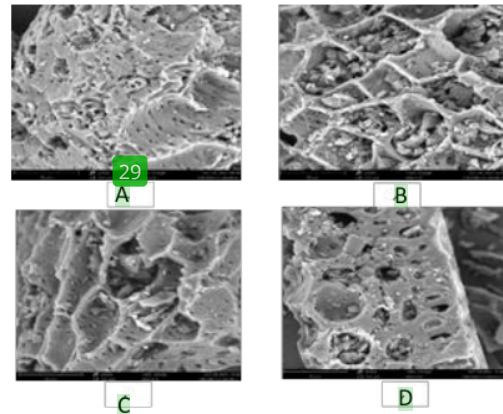


Figure 1. SEM results. (a) bark carbon with KOH activation (b) bark carbon with $ZnCl_2$ activation (c) bark carbon with graded activator Carbon $ZnCl_2 + KOH$ (s) (d) bark carbon with graded activator Carbon $KOH + ZnCl_2$ (s)

In Figure 1(a) the carbon sample of salak bark with KOH activation shows that a large number of evenly distributed pores have been formed on the surface of the sample. In Figure 1(b) the carbon sample of salak bark with $ZnCl_2$ activation shows that pores are formed but the surface tends to be insulated and the number of closed pores is more -compared to the KOH activator. This is because the use of $ZnCl_2$ activator can form a ZnO phase in it. The SEM results of the $ZnCl_2 + KOH$ (s) gradual activator are shown in Figure 1(c). The surface morphology of the sample shows the formation of pores but the number of pores is less and the surface is insulated. Meanwhile, Figure 1(d) shows the SEM results from the surface of the activated carbon of the salak bark with the gradual activator Carbon $KOH + ZnCl_2$ (s). The surface morphology of the sample shows the formation of pores but it is not evenly distributed and has the least number of pores compared to other activator variations. The SEM results show the pore size in the nanoscale. SEM results with gradual activation had fewer pores, were not evenly distributed and tended to agglomerate compared to the activated carbon sample of salak bark which was activated once. In addition, during the carbonization process, nitrogen gas is not flowed, it also affects the uneven distribution of pores on the surface of the activated carbon of the bark(Nurdiansah & Susanti, 2013).

The XRD diffraction pattern of a sample of salak bark carbon powder which was activated once with KOH and $ZnCl_2$ is shown in Figure 1.

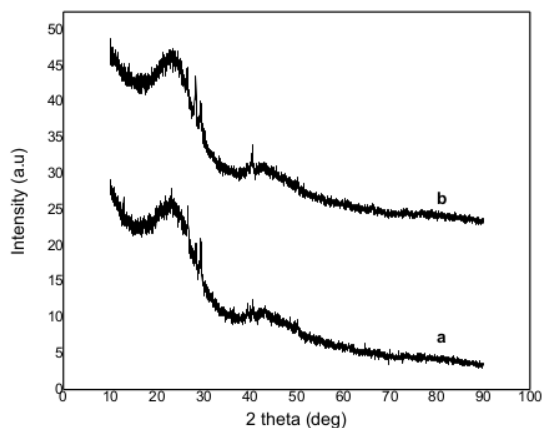


Figure 2 (a) shows the XRD pattern of samples of bark carbon powder activated with KOH , while Figure 1 (b) shows the XRD pattern of samples of bark carbon powder activated with $ZnCl_2$.

Figure 2(a) shows the XRD pattern of salak bark carbon samples with gradual activator of Carbon $ZnCl_2 + KOH(s)$, while in Figure 2(b) shows XRD pattern of salak bark carbon samples which activated gradually with $KOH + ZnCl_2(s)$. From all XRD diffraction results of salak bark carbon powder, an amorphous structure with broad peaks was formed. However, in samples of salak bark carbon powder which was activated once using $ZnCl_2$ activator in Figure 1(a) and salak bark carbon powder which was activated once using KOH activator in Figure 1(b), the diffraction peaks were higher. The increase in the diffraction peak indicates that the degree of crystallinity of the sample of salak bark carbon powder is also getting higher.


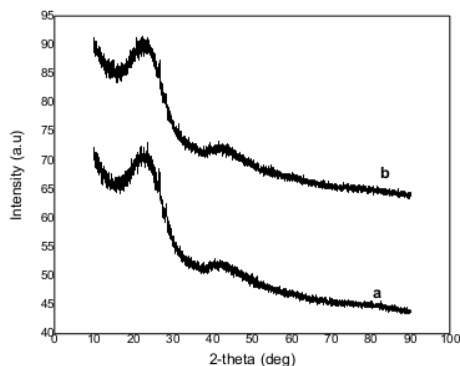


Figure 3. XRD results. (a) bark carbon with graded activator Carbon $ZnCl_2 + KOH(s)$ (b) bark carbon with graded activator Carbon $KOH + ZnCl_2(s)$

The increase in the degree of crystallinity in the sample of salak bark carbon powder is similar to that of graphite, which is the main element of activated carbon. According to Kwieciriska, B, et al (2003) the possible reactions in the formation of graphite are as follows:

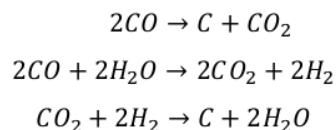

XRD pattern identification results to determine the formed phase using Match! Software is shown in Figure 3.

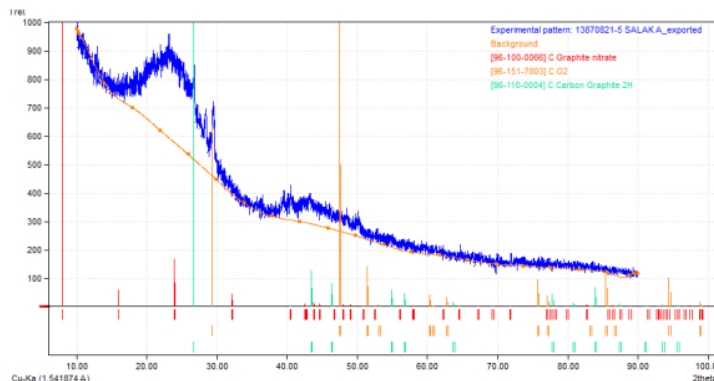


Figure 4. Identification results using the Match! software

In the X-ray diffraction pattern on samples of salak bark carbon powder which was activated once using KOH activator in Figure 1(a) and salak bark carbon powder which was activated once using ZnCl₂ activator in Figure 1(b) showed an amorphous structure at the highest peak at angle at of 26.50°-26.70° indicates the formation of a 2H Carbon Graphite phase with secondary data PDF 96-110-0004. In addition, the sample XRD pattern shows the formation of the Carbon Dioxide phase with secondary data PDF 96-151-7803, which is indicated by a peak at an angle of 28.38°-29.48°. In the XRD pattern, Graphite Nitrate phase is also formed with secondary data PDF 96-100-0066 which shows the highest peak at an angle of 39.56° and 40.49°. Carbon Graphite 2H phase formed has a crystal system and a trigonal R-3m space group. While the Carbon Dioxide phase has a crystal system and space group I-4 2 d tetragonal and Graphite Nitrate which is formed from activated carbon powder has a crystal system and a trigonal R-3m space group. Figure 2(a) shows the XRD pattern of the salak bark carbon sample which is activated in stages, which is activated with ZnCl₂ + KOH(s) and in Figure 2(b) shows the XRD pattern of the salak bark carbon sample which is activated in stages, which is activated with KOH(s) + ZnCl₂ shows an X-ray diffraction pattern, formed an amorphous structure and has a lower diffraction peak. It can be seen that the highest peak is formed from the diminishing X-ray diffraction. The diffraction peak at an angle of 26.50°-26.70° indicates the formation of a 2H Carbon Graphite phase with secondary data PDF 96-110-0004 and an angle of 28.38°-29.48° indicates the formation of a Carbon Dioxide phase with secondary data PDF 96-151-7803. The more gentle the diffraction pattern formed, indicates that the sample has a more amorphous structure.

CONCLUSION

The carbon sample of salak bark with KOH activation shows that a large number of evenly distributed pores have been formed on the surface of the sample. The surface

morphology of the sample shows the formation of pores but the number of pores is less and the surface is insulated. Diffraction results of salak bark carbon powder, an amorphous structure with broad peaks was formed. In addition, the sample XRD pattern shows the formation of the Carbon Dioxide phase with secondary data PDF 96-151-7803, which is indicated by a peak at an angle of 28.38°-29.48°. In the XRD pattern, Graphite Nitrate phase is also formed with secondary data PDF 96-100-0066 which shows the highest peak at an angle of 39.56° and 40.49°. From the carbon structure of the bark formed, it has indicated the formation of activated carbon which is marked by the formation of a graphite structure which is a characteristic of the structure of activated carbon (Rodríguez Correa et al., 2017). Morphology of salak bark carbon samples with KOH activation showed that a large number of uniform pores had been formed on the sample surface. In bark carbon with ZnCl₂ activation, it shows that pores are formed but the surface tends to be insulated and the number of closed pores is more. The surface morphology of the sample from the stratified activator Carbon ZnCl₂ + KOH(s) shows the formation of pores but the number of pores is smaller and the surface is insulated. While the SEM results from the surface of the activated carbon of the bark of bark with activator graded Carbon KOH + ZnCl₂ (s) it appears that pores are formed but are not evenly distributed and have the least number of pores compared to other activators variations. The results of SEM with graded activation had fewer pores, were not evenly distributed and tended to agglomerate compared to the activated carbon sample of salak bark which was activated once.

SUGGESTION

This research has not yet reached the stage of making electrodes, it is hoped that in future research it can be applied to electrodes so that data such as capacity, voltage, current and others are obtained.

ACKNOWLEDGMENTS

We thank the Ministry of Research, Technology and Higher Education DRPM for funding this research. This research is included in the Beginner Lecturer Research Grant scheme for the 2021 Fiscal Year.

REFERENCES (12pt)

- Ajayi, O. A., Olawale, A. S., & others. (2009). A comparative study of thermal and chemical activation of *Canarium Schweinfurthii* Nutshell. *J. Appl. Sci. Res*, 5(12), 2148–2152.
- Bagheri, N., & Abedi, J. (2009). Preparation of high surface area activated carbon from corn by chemical activation using potassium hydroxide. *Chemical Engineering Research and Design*, 87(8), 1059–1064.
- Deiningner, A., Tropentag, D., & others. (2002). *Challenges to organic farming and sustainable land use in the tropics and subtropics: book of abstracts*.
- Fitriana, V. N. (2014). *Sintesis dan karakterisasi superkapasitor berbasis nanokomposit TiO₂/C*.
- Ghosh, A., do Amaral Razzino, C., Dasgupta, A., Fujisawa, K., Vieira, L. H. S., Subramanian, S., Costa, R. S., Lobo, A. O., Ferreira, O. P., Robinson, J., & others. (2019). Structural and electrochemical properties of babassu coconut mesocarp-generated activated carbon and few-layer graphene. *Carbon*, 145, 175–186.

- Habibah, M. D. (2016). Variasi Holding Time Suhu Aktivasi Karbon Aktif dari Tempurung Kluwak (*Pangium edule*) sebagai Elektroda pada Superkapasitor. *Inovasi Fisika Indonesia*, 5(1).
- Hartanto, S., & Ratnawati, R. (2010). Pembuatan karbon aktif dari tempurung kelapa sawit dengan metode aktivasi kimia. *Jurnal Sains Materi Indonesia*, 12(1), 12–16.
- Hendra, D. (2007). Pembuatan arang aktif dari limbah pembalakan kayu puspa dengan teknologi produksi skala semi pilot. *Jurnal Penelitian Hasil Hutan*, 25(2), 93–107.
- Jain, A., Ranjan, S., Dasgupta, N., & Ramalingam, C. (2018). Nanomaterials in food and agriculture: an overview on their safety concerns and regulatory issues. *Critical Reviews in Food Science and Nutrition*, 58(2), 297–317.
- Jin, H., Wang, X., Gu, Z., & Polin, J. (2013). Carbon materials from high ash biochar for supercapacitor and improvement of capacitance with HNO₃ surface oxidation. *Journal of Power Sources*, 236, 285–292.
- Kearns, J. P., Wellborn, L. S., Summers, R. S., & Knappe, D. R. U. (2014). 2, 4-D adsorption to biochars: Effect of preparation conditions on equilibrium adsorption capacity and comparison with commercial activated carbon literature data. *Water Research*, 62, 20–28.
- Kiswandono, A. A. (2014). *STUDY ON THE TRANSPORT OF PHENOL THROUGH CROSSLINKED POLYEUGENOL BASED POLYMER INCLUSION MEMBRANE (PIM)*.
- Lempang, M., Syafii, W., & Pari, G. (2011). Struktur dan komponen arang serta arang aktif tempurung kemiri. *Jurnal Penelitian Hasil Hutan*, 29(3), 278–294.
- Mardwianta, B. (2017). Pembangkitan Energi Listrik Pada Baterai Udara dengan Bahan Karbon Aktif dan Elektrolit Air Laut. *Seminar Nasional Teknologi Informasi Dan Kedirgantaraan (SENATIK) Vol III*.
- Masriatini, R. (2018). Pembuatan Karbon Aktif Dari Kulit Pisang. *Jurnal Redoks*, 2(1), 53–57.
- Mazumdar, P., Pratama, H., Lau, S.-E., Teo, C. H., & Harikrishna, J. A. (2019). Biology, phytochemical profile and prospects for snake fruit: An antioxidant-rich fruit of South East Asia. *Trends in Food Science & Technology*, 91, 147–158.
- Nurdiansah, H., & Susanti, D. (2013). Pengaruh variasi temperatur karbonisasi dan temperatur aktivasi fisika dari elektroda karbon aktif tempurung kelapa dan tempurung Kluwak terhadap Nilai Kapasitansi Electric Double Layer Capacitor (EDLC). *Jurnal Teknik ITS*, 2(1), F13–F18.
- Nurhidayanti, N. (2020). Pemanfaatan Karbon Aktif Dari Tempurung Kelapa Dalam Menurunkan Kadar Amonia Total Dalam Air Limbah Industri. *Pelita Teknologi*, 15(1), 68–76.

- Permata, A. N., Permatasari, R. R. A. P., & Takwanto, A. (2019). STUDI AWAL PENGARUH SUHU DAN KONSENTRASI PADA PROSES AKTIVASI KARBON DARI KAYU HALABAN MENGGUNAKAN ZnCl₂ DAN KOH. *DISTILAT: JURNAL TEKNOLOGI SEPARASI*, 5(2), 141–146.
- Rodríguez Correa, C., Stollovsky, M., Hehr, T., Rauscher, Y., Rolli, B., & Kruse, A. (2017). Influence of the carbonization process on activated carbon properties from lignin and lignin-rich biomasses. *ACS Sustainable Chemistry & Engineering*, 5(9), 8222–8233.
- Sayğlı, H., & Güzel, F. (2016). High surface area mesoporous activated carbon from tomato processing solid waste by zinc chloride activation: process optimization, characterization and dyes adsorption. *Journal of Cleaner Production*, 113, 995–1004.
- Susanti, F., Taer, E., & others. (n.d.-a). *ANALISIS PERBEDAAN BAHAN AKTIVATOR DALAM PEMBUATAN ELEKTRODA SUPERKAPASITOR DARI ARANG TEMPURUNG KELAPA*.
- Susanti, F., Taer, E., & others. (n.d.-b). *ANALISIS PERBEDAAN BAHAN AKTIVATOR DALAM PEMBUATAN ELEKTRODA SUPERKAPASITOR DARI ARANG TEMPURUNG KELAPA*.
- Taer, E., Taslim, R., Putri, A. W., Apriwandi, A., & Agustino, A. (2018). Activated carbon electrode made from coconut husk waste for supercapacitor application. *Int. J. Electrochem. Sci*, 13(12), 12072–12084.
- Waluyo, H. M., Faryuni, I. D., & Muid, A. (2017). Analisis Pengaruh Ukuran Pori Terhadap Sifat Listrik Karbon Aktif Dari Limbah Tandan Sawit Pada Prototipe Baterai. *Jurnal Fisika Flux: Jurnal Ilmiah Fisika FMIPA Universitas Lambung Mangkurat*, 14(1), 27–33.
- Zhou, Y., Fan, M., Chen, L., & Zhuang, J. (2015). Lignocellulosic fibre mediated rubber composites: An overview. *Composites Part B: Engineering*, 76, 180–191.

Activation of ZnCl₂ and KOH Carbon from Bark of Salak Wedi as a Material for Making Supercapacitor Electrodes

ORIGINALITY REPORT

16%

SIMILARITY INDEX

PRIMARY SOURCES

- 1** ocs.unism.ac.id Internet 43 words — 1%
- 2** Imelda Fajriati, Taufiq Aji, Priyagung Dhemi, Dian Aruni Kumalawati, Ria Puspitaningrum. "Purification of used cooking oil of shredded chicken using activated carbon from coconut shell", AIP Publishing, 2023
Crossref 34 words — 1%
- 3** Muhammad Iqbal Al Fuady, Rochmadi Rochmadi, Imam Prasetyo, Teguh Ariyanto. "Surface-Modified Carbon Synthesized from Palm Kernel Shell for Electric Double-Layer Capacitor Applications", Key Engineering Materials, 2021
Crossref 31 words — 1%
- 4** Supriyadi, Suhardi, Masayuki Suzuki, Koichi Yoshida, Tokie Muto, Akira Fujita, Naoharu Watanabe. "Changes in the Volatile Compounds and in the Chemical and Physical Properties of Snake Fruit (Reinw) Cv. during Maturation ", Journal of Agricultural and Food Chemistry, 2002
Crossref 31 words — 1%
- 5** inkalindo-journal.or.id Internet 31 words — 1%
- 6** Yohandri, Debi Rianto, Ananda Putra. "Study of single layer Radar Absorber Material (RAM) based on 30 words — 1%

coconut shell activated carbon", 2017 Progress in Electromagnetics Research Symposium - Fall (PIERS - FALL), 2017

Crossref

-
- 7 pdffox.com 30 words — 1%
Internet
-
- 8 ifory.id 27 words — 1%
Internet
-
- 9 Shimin Wang, Longhai Wang, Taosheng Zhou, Tianjin Zhang, Xinming Xiong, Anxiang Kuang. "Effect of substrates and bottom electrodes on the formation of KTN thin film", Ferroelectrics, 1996 26 words — 1%
Crossref
-
- 10 s-space.snu.ac.kr 24 words — 1%
Internet
-
- 11 D. Duranoğlu, Ü. Beker. "Steam and KOH Activated Carbons from Peach Stones", Energy Sources, Part A: Recovery, Utilization, and Environmental Effects, 2012 18 words — 1%
Crossref
-
- 12 www.dovepress.com 17 words — 1%
Internet
-
- 13 Aulia, Aprilianda, F S Arsyad, A Johan. "Temperature carbonization effect on the quality of activated carbon based on rubber seed shell", Journal of Physics: Conference Series, 2019 16 words — < 1%
Crossref
-
- 14 repository.futminna.edu.ng:8080 16 words — < 1%
Internet

15 Essa, Mohammed Hussein, Muhammad A. Al Zahrani, and Suresh Nesaratnam. "Optimisation of activated carbon production from date pits", *International Journal of Environmental Engineering*, 2013.

Crossref

14 words — < 1%

16 profdoc.um.ac.ir

Internet

13 words — < 1%

17 journal2.uad.ac.id

Internet

12 words — < 1%

18 V. K. M. Katta, R. S. Dubey, G. M. Joshi. "Experimental investigation of activated carbon nanoflakes produced by thermal and chemical activation processes", *Fullerenes, Nanotubes and Carbon Nanostructures*, 2022

Crossref

11 words — < 1%

19 academicjournals.org

Internet

11 words — < 1%

20 ejournal.forda-mof.org

Internet

10 words — < 1%

21 real.mtak.hu

Internet

10 words — < 1%

22 Mika Sillanpää, Chaker Ncibi. "A Sustainable Bioeconomy", *Springer Science and Business Media LLC*, 2017

Crossref

9 words — < 1%

23 Yayuk Astuti, Faisal Aprialdi, Arnelli, Ismoyo Haryanto. "Synthesis of activated carbon/bismuth oxide composite and its characterization for battery electrode", *IOP Conference Series: Materials Science and Engineering*, 2019

9 words — < 1%

-
- 24 electrochemsci.org
Internet 9 words — < 1%
-
- 25 unsri.portalgaruda.org
Internet 9 words — < 1%
-
- 26 Badreddine Belhamdi, Zoulikha Merzougui, Mohamed Trari, Abdelhamid Addoun. "A kinetic, equilibrium and thermodynamic study of l-phenylalanine adsorption using activated carbon based on agricultural waste (date stones)", *Journal of Applied Research and Technology*, 2016
Crossref 8 words — < 1%
-
- 27 Bing Wang, Bin Gao, June Fang. "Recent advances in engineered biochar productions and applications", *Critical Reviews in Environmental Science and Technology*, 2018
Crossref 8 words — < 1%
-
- 28 Leichang Cao, Iris K.M. Yu, Yaoyu Liu, Xiuxiu Ruan et al. "Lignin valorization for the production of renewable chemicals: State-of-the-art review and future prospects", *Bioresource Technology*, 2018
Crossref 8 words — < 1%
-
- 29 W B Kurniawan, A Indriawati, D Marina. " The Effect of Particle Size on the Performance of Electrode Supercapacitor based on Pepper () Shell Activated Carbon ", *IOP Conference Series: Earth and Environmental Science*, 2019
Crossref 8 words — < 1%
-
- 30 moam.info
Internet 8 words — < 1%

EXCLUDE QUOTES OFF

EXCLUDE SOURCES OFF

EXCLUDE BIBLIOGRAPHY ON

EXCLUDE MATCHES OFF